

University of Groningen

## Combinatorial Testing of Supported Catalysts for the Heterogeneous Polymerization of Olefins

Stork, Martin; Herrmann, Andreas; Nemnich, Tanja; Klapper, Markus; Müllen, Klaus

*Published in:*  
Angewandte Chemie International Edition

**IMPORTANT NOTE:** You are advised to consult the publisher's version (publisher's PDF) if you wish to cite from it. Please check the document version below.

*Document Version*  
Publisher's PDF, also known as Version of record

*Publication date:*  
2000

[Link to publication in University of Groningen/UMCG research database](#)

### *Citation for published version (APA):*

Stork, M., Herrmann, A., Nemnich, T., Klapper, M., & Müllen, K. (2000). Combinatorial Testing of Supported Catalysts for the Heterogeneous Polymerization of Olefins. *Angewandte Chemie International Edition*, 39(23), 4367-4369.

### Copyright

Other than for strictly personal use, it is not permitted to download or to forward/distribute the text or part of it without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license (like Creative Commons).

The publication may also be distributed here under the terms of Article 25fa of the Dutch Copyright Act, indicated by the "Taverne" license. More information can be found on the University of Groningen website: <https://www.rug.nl/library/open-access/self-archiving-pure/taverne-amendment>.

### Take-down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Downloaded from the University of Groningen/UMCG research database (Pure): <http://www.rug.nl/research/portal>. For technical reasons the number of authors shown on this cover page is limited to 10 maximum.

# Combinatorial Testing of Supported Catalysts for the Heterogeneous Polymerization of Olefins\*\*

Martin Stork, Andreas Herrmann, Tanja Nemnich, Markus Klapper, and Klaus Müllen\*

Combinatorial chemistry, which has had a high impact on pharmaceutical and biotechnological research and development, has recently also been applied to catalysis research and is strongly connected with the development of high-throughput methods.<sup>[1]</sup> However, few efforts have been directed towards taking advantage of this approach in polymer science.<sup>[2]</sup> Herein we present a novel approach using tagged supports for the testing and direct comparison of silica-<sup>[3]</sup> or polymer-supported<sup>[4]</sup> heterogeneous catalysts for industrial olefin polymerizations.<sup>[5]</sup> In contrast to a process described in the literature<sup>[2c]</sup> which requires a chemical transformation, here direct detection of the different product beads obtained by different catalysts is available through fluorescence. This process accelerates the optimization and standardization of supported catalyst composition, polymerization conditions (e.g. temperature, pressure, and comonomer concentration), and product profiles because standard equipment can be applied.

This truly combinatorial approach starts with the tagging of different catalysts with fluorescent dyes, which exhibit different emission wavelengths. These labeled catalysts are then mixed and introduced into a single polymerization vessel. During the olefin polymerization each catalyst particle forms only one product granule through a particle growth process and can be considered as a microreactor.<sup>[6]</sup>

To assign the different components of the product mixture to the employed catalysts, the polymer products are exposed to UV light. Owing to the different emissions of the labels incorporated in the beads, the resulting products can be directly identified which permits manual separation and characterization. In this way the properties of each of the polymer products can be assigned to the characteristics of the employed catalyst. This protocol is illustrated in Figure 1.

For tagging the catalysts, we chose rylene dyes (see Figure 2) because of their chemical stability, their high tendency to physisorb on silica, and their high fluorescence quantum yields.<sup>[7]</sup> It had to be shown that these dyes do not influence the polymerization and are stable under different polymerization conditions (Table 1).

Catalyst **A**, consisting of metallocene **3** (dimethylsilylbis(2-methylbenzindenyl) zirconocene dichloride; Figure 2), silica-supported and activated with MAO (methylaluminoxane), was tagged with dye **2** (perylene monoimide) and compared with the corresponding untagged catalyst at a range of pressures and temperatures (Table 1). In all cases similar

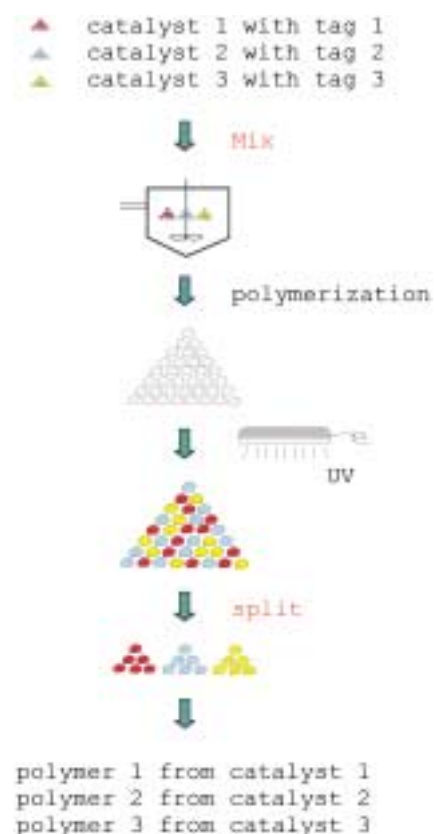


Figure 1. The combinatorial approach.

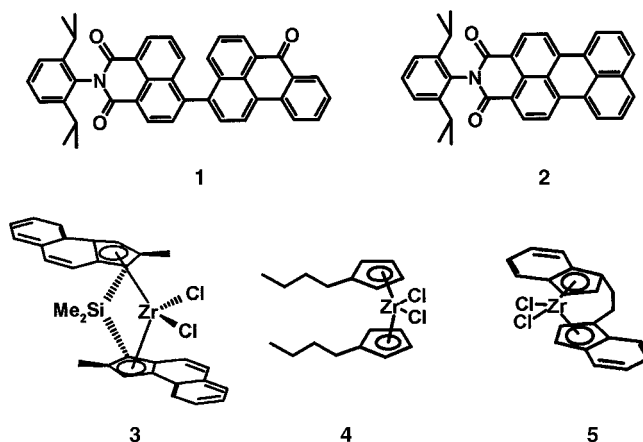


Figure 2. Dyes and catalysts.

Table 1. Comparison of the polymerization behavior of tagged and untagged catalyst **A**.<sup>[a]</sup>

Run	Dye	<i>P</i> [bar]	<i>T</i> [°C]	Productivity [g(PE)g(cat) <sup>-1</sup> h <sup>-1</sup> ]	<i>M<sub>n</sub></i>
1	–	40	70	1180	180 000
2	<b>2</b>	40	70	1220	177 000
3	–	40	50	320	188 000
4	<b>2</b>	40	50	320	194 000
5	–	40	30	60	277 000
6	<b>2</b>	40	30	60	318 000
7	–	20	70	200	78 000
8	<b>2</b>	20	70	200	82 000

[a] *P*: pressure, *T*: polymerization temperature, 5 mL triisobutylaluminum (TIBA).

[\*] K. Müllen, M. Stork, A. Herrmann, T. Nemnich, M. Klapper  
Max-Planck-Institut für Polymerforschung  
Ackermannweg 10, 55128 Mainz (Germany)  
Fax: (+49) 6131-379-350  
E-mail: muellen@mpip-mainz.mpg.de

[\*\*] We thank BASF AG Ludwigshafen for supplying methylaluminoxane and the catalyst **A**.

productivities from the corresponding experiments with and without dye were obtained and the polyethylene samples possessed the same molecular weight and polydispersity as well as the same particle morphology.

The preparation of the catalysts was performed by a facile impregnation method described in the Experimental Section (Figure 3).<sup>[8]</sup>

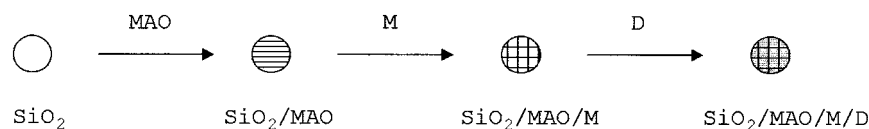


Figure 3. Preparation of labeled catalysts. M = metallocene, D = dye, MAO = methylaluminoxane.

To prove our concept of a combinatorial approach a set of two catalysts was used simultaneously. Catalyst **B** contained bis(*n*-butylcyclopentadienyl)zirconocene dichloride (**4**) with benzanthroneynaphthaleneimide **1** as a tag (Figure 2). Catalyst **C** consisted of ethylene-bis(indenyl)zirconocene dichloride (**5**) and perylenemonoimide **2** (Figure 2). Zirconocene **4** and ansa-zirconocene **5** were selected due to their similar activities. They gave product particles of nearly the same size and thus demonstrated the efficiency of our detection method. On the other hand, the two zirconocenes polymerize ethylene with different molecular weight and polydispersity.

By using catalysts **B** and **C** simultaneously, polyethylene products were obtained (see Experimental Section) as spherical granules within a range of 0.5 to 2 mm diameter. Upon exposure to UV light, particles prepared from the two different catalysts fluoresce with different colors. A fluorescence microscope image (Figure 4) clearly revealed two

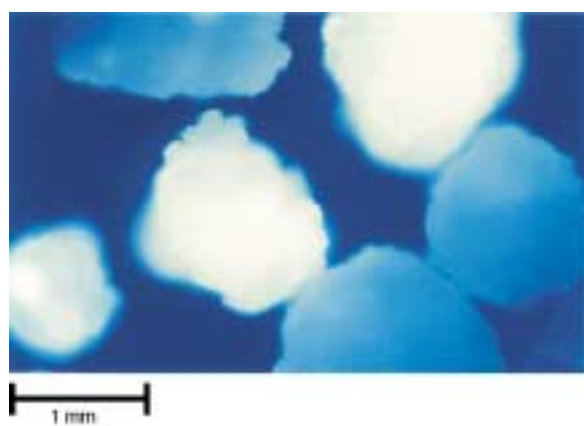


Figure 4. Fluorescence microscope image of the polymer products obtained from the labeled catalysts **B** and **C**.

different kinds of particles: fluorescent and nonfluorescent ones. Owing to the different positions of the absorption maxima and the selection of suitable optical filters, each of the dyes could be excited separately: light with a wavelength of 436 nm only excited **2**, while dye **1** remained dark. The different fluorescence behavior of the dyes allowed an exact assignment of the particles resulting from catalysts **B** and **C**.

For separation, the particles were exposed to UV light of 354 nm and 15 particles (ca. 15 mg) were collected. The amount of polymer collected was sufficient to allow a standard polymer characterization; thus we were able to determine copolymer composition (by NMR spectroscopy), melting temperatures ( $T_m$ ) (by differential scanning calorimetry (DSC) measurements), molecular weights and distributions (by gel permeation chromatography (GPC)) and even crystallinity (by powder diffractometry).

The emission spectra as well as the fluorescence microscope images of the polyethylene samples showed that no migration of labels had occurred. Furthermore, the stability of the dyes under the aggressive reaction conditions with strong Lewis acids and alkylating reagents could be demonstrated.

For each sample the shape of the GPC curves showed a monomodal distribution. Catalyst **B** produced polyethylene with a molecular weight  $M_n$  of 207 000 Da and a molecular weight distribution  $D$  of 2.24; polyethylene from catalyst **C** exhibited almost half the molecular weight  $M_n$  of 124 000 Da and a broad polydispersity  $D$  of 3.47. These results agreed exactly with GPC data obtained from single runs with each catalyst. Additionally, the shape of the GPC curves as well as the values indicated that no exchange of catalyst between the particles took place.

To prove that there is no exchange either of catalyst or of the dyes on the product beads, two different catalysts were used known for having strongly different behavior in the copolymerization of ethylene/hexene. By means of DSC measurements the melting temperatures were used as a probe to determine the amount of incorporated hexene. A migration of the metallocenes should easily be detectable by any deviation from the expected melting temperatures.

Catalyst **D** contained **4** and **2** as a tag. Catalyst **E** consisted of metallocene **3** and was labeled with **1**. Each catalyst system was run separately with and without dye, and then as a mixture. Table 2 indicates that the dye had no influence on  $T_m$ , and that the  $M_n$  values (GPC measurements) were

Table 2. Copolymerization of ethylene/hexene (40 bar, 70 °C, 5 mL TIBA).

	Dye	Zirconocene	$T_m$	$M_n$
<b>D</b>	–	<b>4</b>	129.3	113 000
	<b>1</b>	<b>4</b>	129.9	107 000
<b>E</b>	–	<b>3</b>	119.5	227 000
	<b>2</b>	<b>3</b>	119.0	234 000
mixture of <b>D</b> + <b>E</b>				
particles of <b>D</b>	<b>1</b>	<b>4</b>	129.3	117 000
particles of <b>E</b>	<b>2</b>	<b>3</b>	120.3	221 000

essentially unaffected. This clearly demonstrates that the copolymerization behavior was independent of the dye. More importantly, however, the polymers obtained in the isolated mixture of different tagged product beads have the same properties as in the single experiment.

The concept described herein can be implemented in present polymerization and analytical facilities. The sets of

two catalysts can be easily enlarged because a great variety of rylene dyes covering the whole visible spectra is available.<sup>[9]</sup> Our rapid testing and comparison of supported metallocene catalysts under identical experimental conditions is suitable for other heterogeneous polymerization processes. In order to create larger libraries of heterogeneous catalysts, on-line methods for the detection and characterization of the particles will have to be developed and applied.

### Experimental Section

Procedure for supporting and labeling zirconocenes: All experiments were performed under argon by using standard Schlenk techniques. Catalyst **B**: SiO<sub>2</sub>/MAO (2.50 g, 25 % MAO on silica, TA 02794/HL, Witco GmbH, Bergkamen, Germany) was suspended in toluene (100 mL) followed by addition of **4** (7 mg) in toluene (50 mL) at room temperature and stirred for 2 h. Subsequently, a solution of dye **1** (60 mg) in toluene (50 mL) was added dropwise and the mixture was stirred for 1 h. The almost colorless solution was removed by filtration and the resulting silica/MAO/zirconocene/dye catalyst system was washed twice with toluene and dried in vacuum. Catalysts **C–E** were prepared in a similar way.

Polymerization: General procedure: Two catalysts were mixed and used simultaneously in a single vessel for the polymerization of ethylene. Isobutane (400 mL) and triisobutylaluminum (TIBA) (5 mL; 10 % in n-hexane) were introduced into a Büchi stainless steel reactor (1 L) equipped with a magnetic stirrer and saturated with ethylene (standard conditions: 40 bar, 70 °C). The mixture of catalysts was introduced into the reactor using a pressure gate. After 90 min the polymerization was stopped by releasing the pressure.<sup>[10]</sup>

Received: November 17, 1999

Revised: August 9, 2000 [Z14287]

- [1] a) S. M. Senkan, *Nature* **1998**, *394*, 350; b) P. Cong, R. D. Doolen, Q. Fan, D. M. Giaquinta, S. Guan, E. W. McFarland, D. M. Poojary, K. Self, H. W. Turner, W. H. Weinberg, *Angew. Chem.* **1999**, *111*, 508; *Angew. Chem. Int. Ed.* **1999**, *38*, 484; c) A. Holzwarth, H.-W. Schmidt, W. F. Maier, *Angew. Chem.* **1998**, *110*, 2788; *Angew. Chem. Int. Ed.* **1998**, *37*, 2644; d) M. Orschel, J. Klein, H.-W. Schmidt, W. F. Maier, *Angew. Chem.* **1999**, *111*, 2961; *Angew. Chem. Int. Ed.* **1999**, *38*, 2791; M. T. Reetz, M. H. Becker, H. W. Klein, D. Stöckig, *Angew. Chem.* **1999**, *111*, 1872; *Angew. Chem. Int. Ed.* **1999**, *38*, 1758; e) B. Jandeleit, D. J. Schäfer, T. S. Powers, H. W. Turner, W. H. Weinberg, *Angew. Chem.* **1999**, *111*, 2648; *Angew. Chem. Int. Ed.* **1999**, *38*, 2495.
- [2] a) S. Brocchini, K. James, V. Tangpasuthadol, J. Kohn, *J. Am. Chem. Soc.* **1997**, *119*, 4553; b) X.-D. Xiang, X. Sung, G. Briceno, Y. Lou, K.-A. Wang, H. Chang, W. G. Wallace-Freedman, S.-W. Chen, P. G. Schulz, *Science* **1995**, *268*, 1738; c) T. R. Boussie, C. Coutard, H. Turner, V. Murphy, T. S. Powers, *Angew. Chem.* **1998**, *110*, 3472; *Angew. Chem. Int. Ed.* **1998**, *37*, 3272; d) C. Hinderling, P. Chen, *Angew. Chem.* **1999**, *111*, 2393; *Angew. Chem. Int. Ed.* **1999**, *38*, 2253.
- [3] a) H.-H. Brintzinger, *Angew. Chem.* **1995**, *107*, 1255; *Angew. Chem. Int. Ed. Engl.* **1995**, *34*, 1143; corrigendum: *Angew. Chem.* **1995**, *107*, 1652; *Angew. Chem. Int. Ed. Engl.* **1995**, *34*, 1368; b) H.-H. Brintzinger, D. Fischer, R. Mülhaupt, B. Rieger, R.-M. Waymouth, *Angew. Chem.* **1995**, *107*, 1255; *Angew. Chem. Int. Ed. Engl.* **1995**, *34*, 1143; c) G. Fink, R. Mülhaupt, H.-H. Brintzinger, *Ziegler Catalysts*, Springer, Berlin, **1995**.
- [4] a) S. B. Roscoe, J. M. J. Frechet, J. W. Walzer, A. J. Dias, *Science* **1998**, *280*, 270; b) M. Stork, M. Koch, M. Klapper, K. Müllen, H. Gregorius, U. Rief, *Macromol. Rapid Commun.* **1999**, *20*, 210.
- [5] M. Stork, A. Herrmann, M. Klapper, K. Müllen, DE-B 199 27 483, **1999**.
- [6] a) G. Fink, B. Steinmetz, B. Tesche, C. Przybyla, J. Zechlin, *Acta Polymerica* **1997**, *48*, 392; b) E. Bonini, V. Fraaije, G. Fink, *J. Polym. Sci. Part A* **1995**, *3*, 2393.

- [7] F. O. Holtrup, G. R. J. Müller, H. Quante, S. DeFeyer, F. C. De-Schryver, K. Müllen, *Chem. Eur. J.* **1997**, *3*, 219.
- [8] A. Herrmann, M. Stork, K. Müllen, DE-B 199 27 482, **1999**.
- [9] a) For a review see: H. Langhals, *Heterocycles* **1995**, *40*, 477; b) L. Feiler, H. Langhals, K. Polborn, *Liebigs Ann.* **1995**, 1229; c) H. Quante, K. Müllen, *Angew. Chem.* **1995**, *107*, 1487; *Angew. Chem. Int. Ed. Engl.* **1995**, *34*, 1323; d) F. O. Holtrup, G. R. J. Müller, J. Uebe, K. Müllen, *Tetrahedron* **1997**, *53*, 6847; e) U. Rohr, P. Schlichting, A. Böhm, M. Gross, K. Meerholz, C. Bräuchle, K. Müllen, *Angew. Chem.* **1998**, *110*, 1463; *Angew. Chem. Int. Ed.* **1998**, *37*, 1434.
- [10] All polymerization experiments presented herein were repeated at least two times to prove the reproducibility.

## An Allosteric Ribozyme Regulated by Doxycycline\*\*

Nicolas Piganeau, Andreas Jenne, Vincent Thuillier,\* and Michael Famulok\*

Specific ligand-binding nucleic acid molecules (aptamers) can be isolated by searching the “shape-space” of vast combinatorial nucleic acid libraries for functional sequences in vitro.<sup>[1–3]</sup> Selection strategies for the isolation of aptamers usually involve incubation of a complex library of nucleic acids with the immobilized target molecule or the immobilization of a preformed target/nucleic acid complex.

A considerable number of RNA aptamers that bind a variety of targets with high affinity and specificity have been isolated and extensively characterized. Detailed structural investigations of many aptamer/ligand complexes have established that complex formation in most cases is accompanied by extensive conformational changes only in the presence of the cognate ligand by adaptive binding events.<sup>[4–11]</sup> This property of small-molecule-binding aptamers allowed the rational design of artificial allosteric ribozymes inhibited or activated by a ligand that is bound to an aptamer which has been positioned in immediate proximity to a ribozyme sequence.<sup>[12–15]</sup>

We have applied a novel in vitro selection strategy based on allosteric inhibition of a hammerhead ribozyme fused to a

[\*] Prof. Dr. M. Famulok, N. Piganeau,<sup>[+]</sup> Dr. A. Jenne  
Kekulé-Institut für Organische Chemie und Biochemie  
Gerhard Domagk-Strasse 1, 53121 Bonn (Germany)  
Fax: (+49) 228-735388  
E-mail: m.famulok@uni-bonn.de  
Dr. V. Thuillier  
Aventis Gencell  
3825 Bay Center Place  
Hayward, CA 94545 (USA)  
Fax: (+1) 510-887-1680  
E-mail: vincent.thuillier@aventis.com

[+] New address: Aventis Gencell, 3825 Bay Center Place, Hayward, CA 94545 (USA)

[\*\*] This work was supported by Aventis Gencell and by a grant from the Volkswagen Foundation (Priority program “conformational control”) to M.F. We thank M. Blind, G. Mayer, D. Proske, and G. Sengle (Universität Bonn) for helpful discussions as well as J. Crouzet, J. F. Mayaux, and M. Finer (Aventis Gencell) for support.